

Absorption of BN nanotubes under the influence of a perpendicular electric field

Claudio Attaccalite^{*1}, Ludger Wirtz^{1,2}, Andrea Marini³, and Angel Rubio^{4,2}

¹ Institute for Electronics, Microelectronics, and Nanotechnology (IEMN), Dept. ISEN, B.P. 60069, 59652 Villeneuve d'Ascq Cedex, France

² European Theoretical Spectroscopy Facility (ETSF), San Sebastián, Spain

³ Istituto Nazionale per la Fisica della Materia e Dipartimento di Fisica dell'Università di Roma "Tor Vergata", Via della Ricerca Scientifica, I-00133 Roma, Italy

⁴ Donostia International Physics Center (DIPC) and Department of Material Physics, UPV/EHU and Centro Mixto CSIC-UPV, 20018 San Sebastián, Spain

Key words BN nanotubes, optical absorption, excitons, band gap, defect states

PACS 71.35.-y, 61.46.+w, 81.07.De

We calculate the optical absorption spectra of prototype (6,6) and (9,9) BN nanotubes in the presence of a perpendicular electric field. This model mimics a gated BN nanotube device. Even though the band-gap of the tubes decreases strongly as a function of the electric field strength, the absorption spectrum remains remarkably constant up to high field-strength. On the contrary, we show that the levels which are responsible for defect-mediated photo-luminescence are shifted by the electric field. We address the use of BN nanotubes for optoelectronic applications.

Copyright line will be provided by the publisher

1 Introduction

Contrary to carbon nanotubes, boron nitride nanotubes (BNNTs), have a large band-gap of more than 6 eV, independently of radius and chirality [1]. Recently, the potential of bulk hexagonal BN for ultraviolet lasing has been demonstrated [3]. It is a logical next step trying to build lasing or opto-electronic devices with BN nanotubes. In this respect, it is interesting to know if the optical properties can be tuned in a controlled way. It has been shown theoretically [4, 5] that the band gap of BNNTs can be reduced by applying an electric field perpendicular to the tube axis. This decrease of the gap is due to the Stark-Effect, i.e., the charge densities of the highest occupied molecular orbital (HOMO) and the lowest unoccupied molecular orbital (LUMO) become spatially separated on opposite sides of the tube [4]. Even though the gap is reduced considerably, the effect of an electric field on the optical absorption spectrum was found to be less pronounced [6] (for light polarization parallel to the tube axis which gives the dominant contribution to the averaged light-scattering cross section). The calculations of Ref. [6] have been performed on the level of the random-phase approximation, i.e., neglecting the effects of electron-electron and electron-hole correlation (excitonic effects). These effects, however, have been shown to strongly dominate the optical spectra of BNNTs [7, 8]. We investigate therefore in this paper, how the transverse electric field changes the excitonic nature of the absorption spectrum. Furthermore, we discuss the influence of the electric field on the impurity levels that may lead to defect-mediated luminescence [9].

* Corresponding author: e-mail: Claudio.Attaccalite@gmail.com

2 Methodology

The calculations of the optical absorption spectra proceed in three steps. We first calculate the wavefunctions of the valence band states and a large number of conduction band states using density functional theory (DFT) in the local-density approximation (LDA). These calculations have been done using the Quantum-ESPRESSO package [10]. Core electrons are replaced by pseudo-potentials and the wavefunctions are expanded in plane waves with an energy cutoff at 40 Rydberg. We use a periodic supercell where the closest distance between neighboring tubes is 10.6 Å. The transverse electric field is introduced by a sawtooth potential commensurate with the supercell geometry. The optimized geometry of the tube was only calculated without the external electric field.

The second and third step are analogous to the recent work on excitonic effects in BN nanotubes [7, 8]: We use the GW-approximation [11, 12] to calculate the quasi-particle energies (“true” single-particle excitation energies). Effects of electron-hole attraction (excitonic effects) are included by solving the Bethe-Salpeter (BS) equation [11]. These calculations are performed with the code SELF [13].

For the present exploratory calculations we have chosen the (9,9) BN tube which has a diameter of 12.5 Å, at the lower limit of the diameter range of experimentally produced single-walled BNNTs. For the investigation of excitonic effects, we have chosen - due to reasons of numerical feasibility - the (6,6) BN tube which has a diameter of 8.3 Å. Note that this latter tube is only 0.3 Å larger in diameter than the (10,0) tube that was investigated in Ref. [6]. The effect of an electric field should thus be practically the same.

3 Results and discussion

Fig. 1 shows the band-structure of the (9,9) BNNT for different values of the external electric field. We note that the gap for this tube is indirect because the “nearly-free electron” (NFE) state [2] at Γ is lower in energy than the conduction band minimum at the direct gap which is situated at $2/3$ between Γ and X . However, for larger diameter armchair tubes, the NFE state is higher in energy and the onset of absorption is thus determined by the value of the direct gap (i.e., we do not need to consider phonon mediated absorption for indirect gap materials here). Fig. 1 demonstrates that the band-gap becomes strongly reduced through the application of a perpendicular electric field as shown in previous works [4, 5, 6].

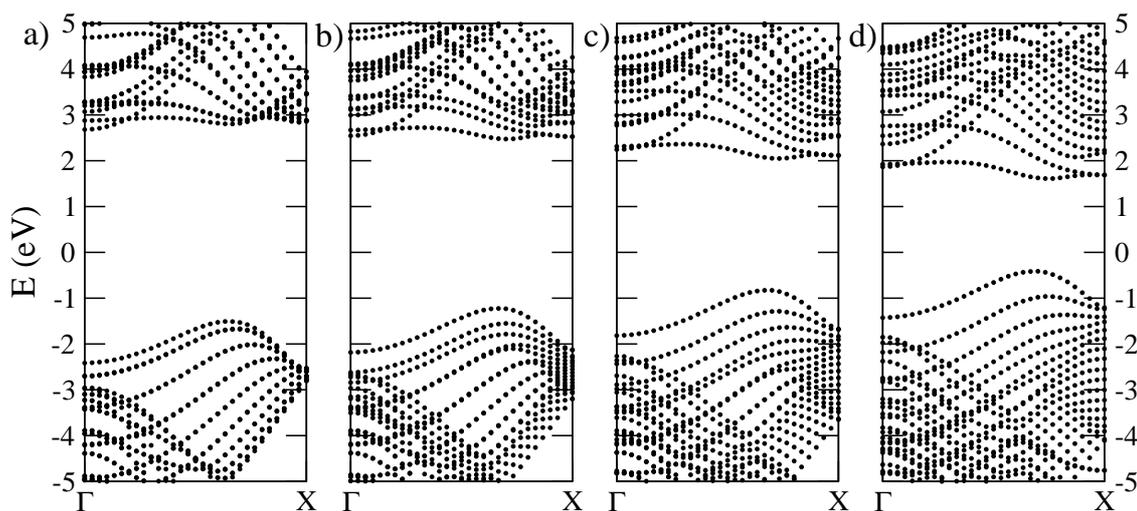


Fig. 1 Calculated band structure of a (9,9) BN nanotube, a) without external electric field, b) $E = 0.1 \text{ V/\AA}$, b) $E = 0.1 \text{ V/\AA}$, c) $E = 0.2 \text{ V/\AA}$, d) $E = 0.3 \text{ V/\AA}$.

Fig. 2 shows the optical spectra that result from the band-structures of Fig. 1 in the random-phase approximation. In this approximation, the effects of electron-electron and electron-hole correlation are neglected and the spectrum is calculated according to Fermi's golden rule:

$$\epsilon_2(\omega) \propto \int_{\text{1BZ}} dk \sum_{v,c} |D_{vk,ck}|^2 \delta(\epsilon_{ck} - \epsilon_{vk} - \omega), \quad (1)$$

where the integral is performed over the first Brillouin zone, v and c denote valence and conduction bands, respectively. $D_{vk,ck}$ denotes the dipole matrix element between two states with energies ϵ_{ck} and ϵ_{vk} , respectively. We only show here the absorption spectra for light polarization parallel to the tube axis as this contribution dominates the total absorption cross section. (The contribution of perpendicularly polarized light is strongly suppressed by depolarization effects below 7 eV [14].) The main peak at 5.3 eV in the spectrum corresponds to the maximum in the joint density of states for transitions between the π and π^* bands of the BN single sheet at M . The fine structure below this peak in the spectrum without electric field is caused by Van-Hove singularities due to the formation of one dimensional subbands in the tubes. With increasing electric field, this fine-structure is washed out. The main peak around 5.4 eV remains almost constant. With increasing electric field, the onset of absorption is shifted towards lower energies. However, due to the spatial separation of occupied and unoccupied states on different sides of the tube, the spectral weight at the onset of absorption is very weak. Therefore, the overall spectrum remains remarkably stable as a function of the electric field. This is in agreement with the findings of Ref. [6].

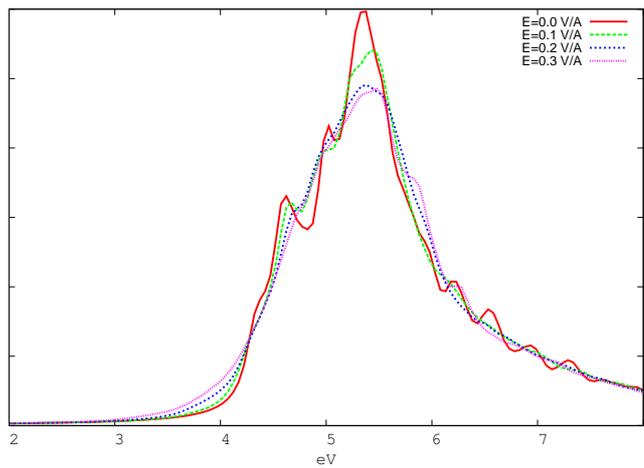


Fig. 2 Optical spectrum, calculated in the random-phase approximation, of the (9,9) BN nanotube for different values of a perpendicular homogeneous electric field. The light-polarization is parallel to the tube axis.

The main result of this paper is the inclusion of quasi-particle and excitonic effects on the absorption spectra shown in Fig. 3. For comparison with experimental data, we present the data with a broadening of 0.1 eV in the left panel. For a theoretical discussion, we also present the spectra with a very fine broadening of 0.01 eV, in order to better discern the distinct excitonic peaks. The effect of the electric field is a shift of oscillator strength from the dominant excitonic peak to the higher lying excitonic peaks. Nevertheless, as in the case of the RPA spectra, the overall structure of the spectrum remains constant. We note that the blue shift of the spectrum for higher field-strength is due to an enhanced value of the GW gap correction. However, this shift depends on the size of the supercell. We expect the shift to be less pronounced for increasing cell size, i.e., larger distances between the tubes. In principle, a cutoff of the Coulomb-potential between neighboring tubes should be used [15, 16].

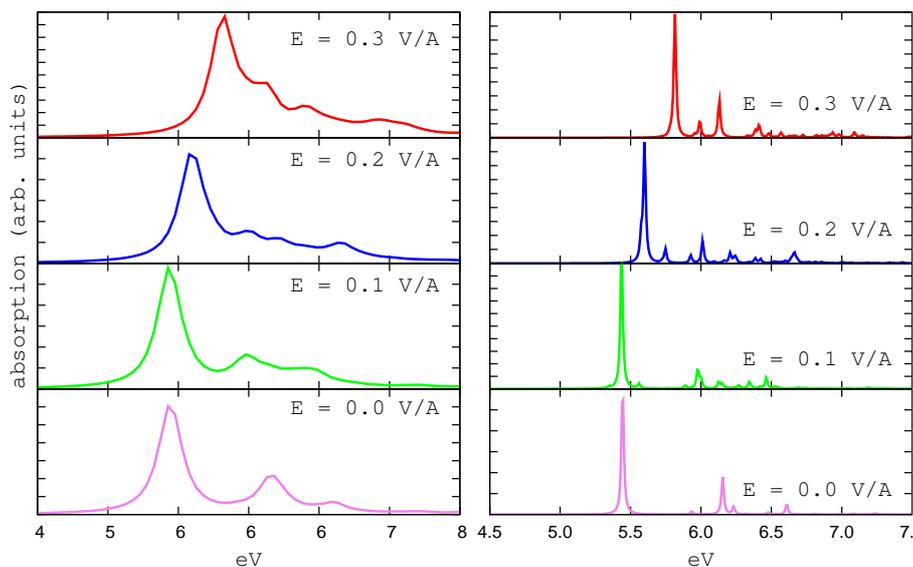


Fig. 3 Optical spectrum including quasi-particle and excitonic effects of the (6,6) BN nanotube for different values of a perpendicular homogeneous electric field: a) no electric field, b) 0.1 V/Å, c) 0.2 V/Å, d) 0.3 V/Å. The light-polarization is parallel to the tube axis. Left panel: 0.1 eV broadening, right panel: 0.01 eV broadening.

For pure BN nanotubes, we can thus conclude that the optical absorption spectra are very little effected by an electric field. This situation may, however, change for luminescence spectra. Peaks around 4 eV in the luminescence spectra [9] are related to defect levels. Possible candidates are vacancies or carbon substitutions. As an example, we have calculated the influence of the electric field on the acceptor level that is due to the replacement of a nitrogen atom by a carbon atom. We have performed the calculation in a large supercell, containing one carbon substitution in 252 atoms. Fig. 4 a) shows the density of states of the pure (9,9) BNNT, calculated within DFT-LDA. Adding the carbon impurity in panel b) introduces an impurity level at about 0.5 eV above the valence band edge. Depending on the orientation of the carbon impurity with respect to the direction of the electric field, this impurity level can move up or down with respect to the valence and conduction band edges (Fig. 4 c and d). Photoluminescence may involve transitions from the conduction band to the impurity level and from the impurity level to the valence band. Defect mediated luminescence spectra may thus be more sensitive to the influence of an electric field than the spectra of pure BNNTs.

4 Conclusion

In conclusion, we have shown that the optical spectra of BN nanotubes are quite robust to the application of external fields. Furthermore, we have shown that the external field affects the defect energy levels due to carbon impurities. Those defects gives rises to luminescence in the visible as well as modification of the shape of the main absorption peak shown in Fig. 3. Therefore an external electric field can be used as tool to discriminate the photoemission due to exciton recombination in pure systems with respect to the one due to defects. BN nanotubes may thus be very good candidates for tunable nanoscale optoelectronic devices in the UV regime.

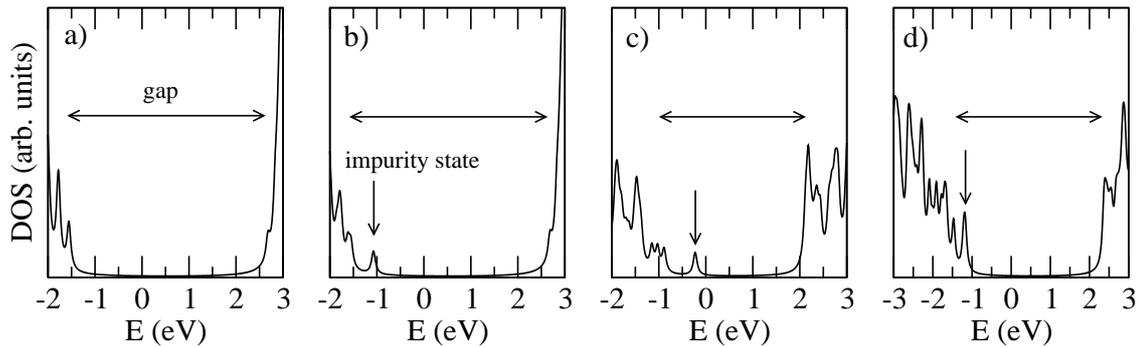


Fig. 4 Density of states of a) a pure (9,9) BN nanotube, b) a tube with a Carbon impurity atom, c) with a C atom and a perpendicular E-field of 0.2 V/\AA , d) with a C atom on the opposite side and an E-field of 0.2 V/\AA . The light-polarization is parallel to the tube axis.

Acknowledgements This work has been funded by the EC Network of Excellence NANOQUANTA (ref. NMP4-CT-2004-500198). C.A. and L.W. acknowledge support from the French national research agency (ANR). A.R. acknowledges support from the Spanish Ministry of Education, the SANES (ref. NMP4-CT-2006-017310), DNA-NANODEVICES (ref. IST-2006-029192), and NANO-ERA Chemistry projects, the University of the Basque Country EHU/UPV (SGIker Arina), and the Basque Country Government. We thankfully acknowledge the computer resources, technical expertise and assistance provided by the Barcelona Supercomputing Center.

References

- [1] The band-gap calculated in the widely used local-density approximation as published in the first papers on BN nanotubes [2] is about 4.5 eV. Only for very small nanotubes, the gap can have smaller values. Recent calculations of the quasi-particle band-structure [7, 8] demonstrate that the gap is larger than 6 eV.
- [2] A. Rubio, J. L. Corkill, and M. L. Cohen, *Phys. Rev. B* **49**, R5081 (1994); X. Blase, A. Rubio, S. G. Louie, and M. L. Cohen, *Europhys. Lett* **28**, 335 (1994).
- [3] K. Watanabe, T. Taniguchi, and H. Kanda, *Nature Materials* **3**, 404 (2004).
- [4] K.H. Koo, M.S.C. Mazzoni, and S.G. Louie, *Phys. Rev. B* **69**, 201401(R) (2004).
- [5] C.-W. Chen, M.-H. Lee, and S.J. Clark, *Nanotechnology* **15**, 1837 (2004).
- [6] C.-W. Chen, M.-H. Lee, and Y.-T. Lin, *Appl. Phys. Lett.* **89**, 223105 (2006).
- [7] L. Wirtz, A. Marini, and A. Rubio, *Phys. Rev. Lett.* **96**, 126104 (2006).
- [8] C.-H. Park, C.D. Spataru, S.G. Louie, *Phys. Rev. Lett.* **96**, 126105 (2006).
- [9] M.G. Silly, P. Jaffrennou, J. Barjon, J.S. Lauret, F. Ducastelle, A. Loiseau, E. Obraztsova, B. Attal-Tretout, and E. Rosencher, *Phys. Rev. B* **75**, 085205 (2007).
- [10] S. Baroni, A. Dal Corso, S. de Gironcoli, P. Giannozzi, C. Cavazzoni, G. Ballabio, S. Scandolo, G. Chiarotti, P. Focher, A. Pasquarello, K. Laasonen, A. Trave, R. Car, N. Marzari, A. Kokalj, <http://www.pwscf.org/>.
- [11] For a recent review see, e.g., G. Onida, L. Reining, and A. Rubio, *Rev. Mod. Phys.* **74**, 601 (2002).
- [12] M.S. Hybertsen and S.G. Louie, *Phys. Rev. B* **34**, 5390 (1986).
- [13] A. Marini et al., the SELF project, <http://www.fisica.uniroma2.it/~self/>
- [14] A. G. Marinopoulos, L. Wirtz, A. Marini, V. Olevano, A. Rubio, and L. Reining, *Appl. Phys. A* **78**, 1157 (2004).
- [15] C. D. Spataru, S. Ismail-Beigi, L. X. Benedict, and S. G. Louie, *Phys. Rev. Lett.* **92**, 077402 (2004); *Appl. Phys. A* **78**, 1129 (2004).
- [16] C.A. Rozzi, D. Varsano, A. Marini, E.K.U. Gross, and A. Rubio, *Phys. Rev. B* **73**, 205119 (2006).