

Unraveling the Impact of Halide Mixing on Perovskite Stability

Jeremy Hieulle^{1,‡}, Xiaoming Wang^{2,‡}, Collin Stecker¹, Dae-Yong Son¹, Longbin Qiu¹, Robin Ohmann^{1,†}, Luis K. Ono¹, Aitor Mugarza^{3,4}, Yanfa Yan^{2,*}, and Yabing Qi^{1,*}

¹Energy Materials and Surface Sciences Unit (EMSSU), Okinawa Institute of Science and Technology Graduate University (OIST), 1919-1 Tancha, Onna-son, Okinawa 904-0495, Japan.

²Department of Physics and Astronomy and Wright Center for Photovoltaics Innovation and Commercialization, The University of Toledo, Toledo, Ohio 43606, United States.

³Catalan Institute of Nanoscience and Nanotechnology (ICN2), Consejo Superior de Investigaciones Científicas (CSIC) and The Barcelona Institute of Science and Technology, Campus UAB, Bellaterra, 08193 Barcelona, Spain.

⁴ICREA–Institutió Catalana de Recerca i Estudis Avançats, 08010 Barcelona, Spain.

ABSTRACT: Increasing the stability of perovskites is essential for their integration in commercial photovoltaic devices. Halide mixing is suggested as a powerful strategy toward stable perovskite materials. However, the stabilizing effect of the halides critically depends on their distribution in the mixed compound, a topic that is currently under intense debate. Here we successfully determine the exact location of the I and Cl in the mixed $\text{CH}_3\text{NH}_3\text{PbBr}_{3-y}\text{I}_y$ and $\text{CH}_3\text{NH}_3\text{PbBr}_{3-z}\text{Cl}_z$ perovskite lattices and correlate it with the enhanced stability we find for the latter. By combining scanning tunneling microscopy (STM) and density functional theory (DFT), we predict that for low ratios, iodine and chlorine incorporation have opposite effects on the electronic properties and stability of the $\text{CH}_3\text{NH}_3\text{PbBr}_3$ perovskite material. In addition, we determine an ideal halide ratio for stability increase without detrimental bandgap modification, providing an important direction for the fabrication of stable perovskite devices. The increased material stability induced by chlorine incorporation is verified by performing photoelectron spectroscopy on a device architecture. Our findings provide an answer to the current debate on halide incorporation and demonstrate their direct influence on device stability.

INTRODUCTION

Metal halide perovskite materials have been the focus of intense investigation due to their low cost and superior photovoltaic performance, with record power conversion efficiencies exceeding 23.7%¹. Despite numerous advantages, their poor stability hinders commercialization of perovskite-based devices. To increase perovskite stability various strategies have been envisaged^{2,3}. Mixing different halides (I, Br, Cl) has been shown both experimentally and theoretically to have a strong impact on the device performance and stability⁴⁻⁹. For example, a small addition of bromine¹⁰ or chlorine¹¹ confers increased device stability compared to pure iodide ($\text{CH}_3\text{NH}_3\text{PbI}_3$) based devices. Addition of Cl to $\text{CH}_3\text{NH}_3\text{PbBr}_3$ films improves carrier recombination lifetime¹² and increases open circuit voltage^{13,14}. However, the role of Cl and the extent of its incorporation into the crystal lattice remain a topic of debate, with conflicting results reported in the literature¹⁵⁻²¹.

Here, we choose to mix $\text{CH}_3\text{NH}_3\text{PbBr}_3$ perovskite with two different halides, I and Cl, that have different ionic radii and bond strengths with Pb. In this way, the effect of the incorporation of a larger ion (I > Br) and a smaller ion (Cl < Br) can be addressed. In this work, combining scanning tunneling microscopy (STM), density functional theory (DFT) and UV/x-ray photoelectron spectroscopy (UPS/XPS), we reveal the exact location of I and Cl anions in the perovskite structure at the atomic scale, and demonstrate the impact of halide-incorporation on the material electronic properties and stability.

Furthermore, we determine the ideal Cl-incorporation ratio for stability increase without detrimental bandgap modification.

Despite the great capability of STM and UPS as demonstrated in the current study, it is important to realize that there are some limitations associated with such surface sensitive characterization techniques. Combined with suitable DFT calculations, STM can be used to investigate mainly the surface and possibly also the sub-surface structures of perovskite materials. The probing depth of photoelectron spectroscopy (PES) depends on the energy of photoelectrons, but in general it is still considered to be surface sensitive as it can only probe up to approximately 5 nm of the top surface of the sample. Therefore, our current surface science study is *not* an attempt to provide a full picture of what it is happening in the bulk material of a solar cell device. On the other hand, although our results may not accurately represent the grain interior of perovskite as in real solar cell absorbers, our study does offer valuable insights on other aspects such as surface/interface properties. Several studies have reported that surface/interface properties themselves play an important role in determining perovskite solar cell performance²²⁻²³. For example, it has been shown that the interface between the perovskite film and the hole transport layer (HTL) is crucial for achieving high solar cell device performance²⁴⁻²⁷. The aim of our current study combining the use of STM, DFT calculations, and PES is therefore to obtain a better understanding of these interfacial properties by examining their electronic structure and morphology with an unprecedented high resolution.

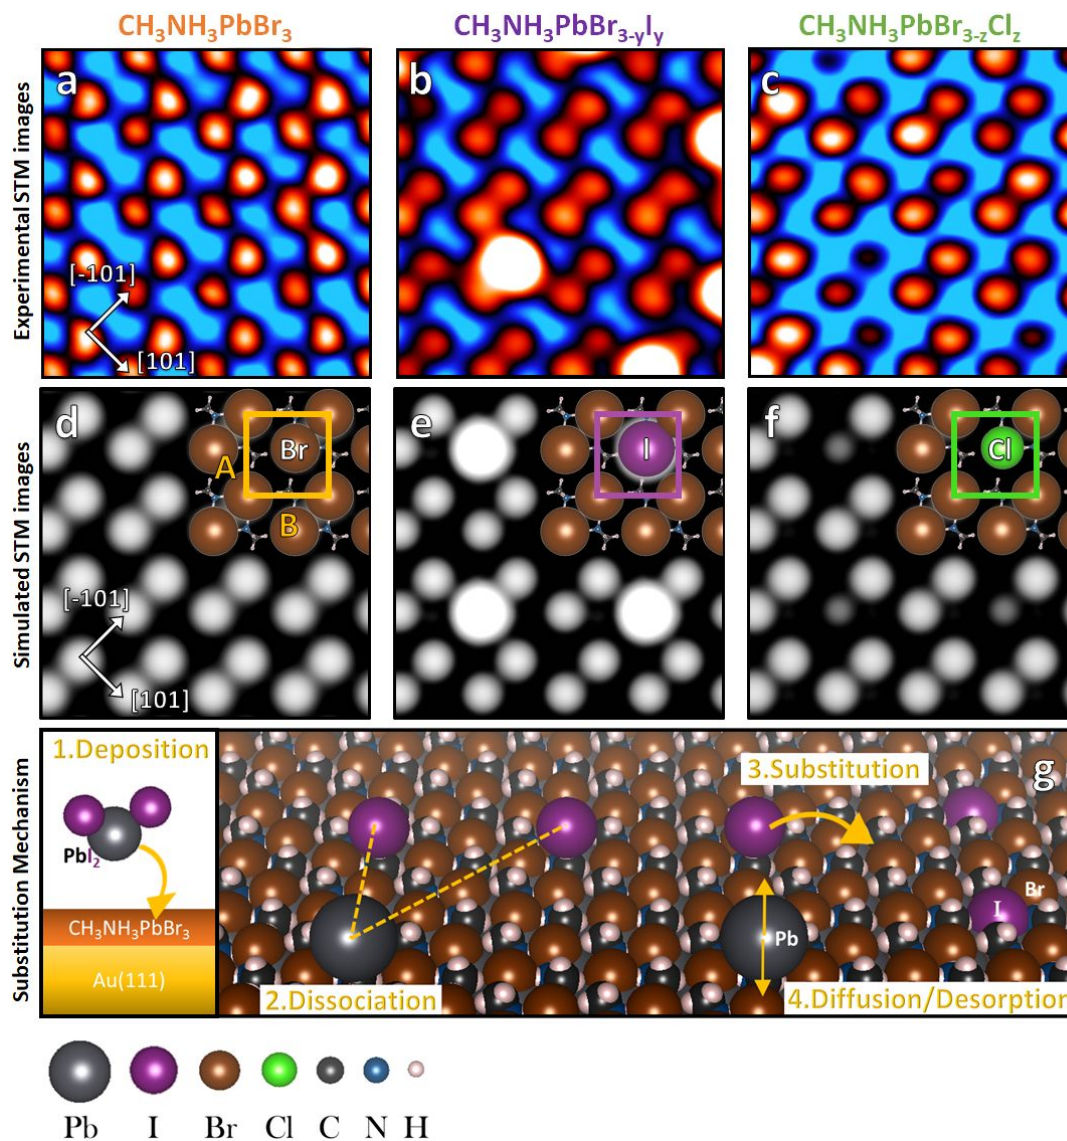


Figure 1. Halide substitution at the perovskite surface. a-c Scanning tunneling microscopy images of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ (a), $\text{CH}_3\text{NH}_3\text{PbBr}_{3-y}\text{I}_y$ (b), and $\text{CH}_3\text{NH}_3\text{PbBr}_{3-z}\text{Cl}_z$ (c) perovskite surfaces. d-f Calculated (010) surface of the mixed halide organic-inorganic perovskites. Inset: Corresponding surface structure and unit-cell. The lattice unit-cell of pristine $\text{CH}_3\text{NH}_3\text{PbBr}_3$ is square with the following parameters: $A = B = 7.4 \text{ \AA}$ and was found to not be altered by the deposition of PbI_2 or PbCl_2 molecules. The size of Br, I and Cl ions were multiplied by a factor of 4.5 for better visibility. g) Scheme of the substitution mechanism occurring at the surface of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ perovskite after deposition of PbI_2 or PbCl_2 molecules (Only the PbI_2 case is presented for clarity, but PbCl_2 is following the same mechanism). Image parameters: (a) Bias = +1.3 V, Current = 80 pA; (b) +2.0V, 120 pA; (c) -1.9V, 19 pA; Image size: (a-c) 2.3 nm x 2.3 nm.

RESULTS AND DISCUSSION

$\text{CH}_3\text{NH}_3\text{PbBr}_3$ perovskite thin films were prepared on a clean Au(111) surface²⁸ via molecular beam epitaxy in an ultrahigh vacuum environment (see methods). The thickness of the ultra-thin film was approximately $4 \pm 1 \text{ nm}$. Scanning tunneling microscopy images reveal a pair motif similar to the characteristic surface reconstruction previously observed for $\text{CH}_3\text{NH}_3\text{PbBr}_3$ single crystals²⁹⁻³¹ showing the (010) surface termination (Figure 1a). The bright spots in the STM images correspond to bromine ions of the top layer perovskite structure. For pure $\text{CH}_3\text{NH}_3\text{PbBr}_3$ all the bromine ions have the same height and width in the STM topographs.

Thereafter, PbI_2 or PbCl_2 was deposited on the pure $\text{CH}_3\text{NH}_3\text{PbBr}_3$ film kept at room temperature (see Methods). Distinct protrusions with different apparent height and width

appear in the perovskite films (Figures 1b, 1c). After deposition of PbI_2 , strong bright spots appear with an estimated height of $40 \pm 10 \text{ pm}$ higher than the surrounding Br ions and with larger diameters (Figure 1b). In contrast, after PbCl_2 deposition, slightly darker spots are evident, with smaller diameters and a lower apparent height (Figure 1c). These dark spots appear $20 \pm 10 \text{ pm}$ lower than the neighboring bromine ions.

To unravel the origin of the dark and bright protrusions observed at the surface of the perovskite films, we performed DFT calculations. The atomic structures, as well as the projected density of states (PDOS), of the perovskite films were determined using the VASP code (see Methods). First the pair structure of the (010) top layer surface of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ perovskite was reproduced using DFT and taken as a reference (Figure 1d). Thereafter the impact of PbI_2 and PbCl_2 deposition on the atomic structure of the perovskites was further addressed

by DFT. Different scenarios were considered such as, the adsorption of the entire $\text{PbI}_2/\text{PbCl}_2$ molecules (Figure S1), as well as the adsorption (Figure S2) or substitution of Pb, I, and Cl at the $\text{CH}_3\text{NH}_3\text{PbBr}_3$ surface (Figure 1). The best match between the STM experimental results and DFT simulation is found for the dissociation of the PbI_2 (or PbCl_2) molecule, followed by the substitution of Br by I (or Cl). The schematic drawing for the iodine case is shown in Figure 1g as an example. We thus assign the bright and dark protrusions observed in our STM experiment respectively to I and Cl ions, that substitute Br ions at the surface of the perovskite film (Figures 1e, 1f). These scenarios are the most energetically favorable ones, and the corresponding simulated STM images best reproduce our experimental data (supplementary note 1). Thus, by depositing PbI_2 or PbCl_2 on a pristine $\text{CH}_3\text{NH}_3\text{PbBr}_3$ film, two different mixed-halide perovskites, $\text{CH}_3\text{NH}_3\text{PbBr}_{3-y}\text{I}_y$ and $\text{CH}_3\text{NH}_3\text{PbBr}_{3-z}\text{Cl}_z$, were formed.

Large-scale STM images (Figures 2a-c) of the surface topography show that the additional bright and dark spots

observed after PbI_2 and PbCl_2 deposition are randomly distributed at the surface of the perovskite films without any long-range order (Figures 2b, 2c). These findings are supported by the Fast Fourier Transform (FFT) of the STM images, which do not show any additional peak at low k-values for the mixed perovskite compared to pristine $\text{CH}_3\text{NH}_3\text{PbBr}_3$ (insets in Figures 2a-c). The distribution of the different apparent heights that are measured at the surface of the three films is given in Figures 2d-f. While for the pristine perovskite only a single peak is present corresponding to Br ions, additional peaks show up for the mixed halide perovskites corresponding to I and Cl ions, respectively. Surprisingly, the substitution of Br by I or Cl does not significantly change the lattice unit cell (i.e., lateral structure) of the perovskite surface. However, the vertical positions of the I and Cl were found to be different than the Br ions in pristine $\text{CH}_3\text{NH}_3\text{PbBr}_3$ (Figures 2g-i). The iodine ions are slightly upshifted with respect to the Br plane (Figure 2h).

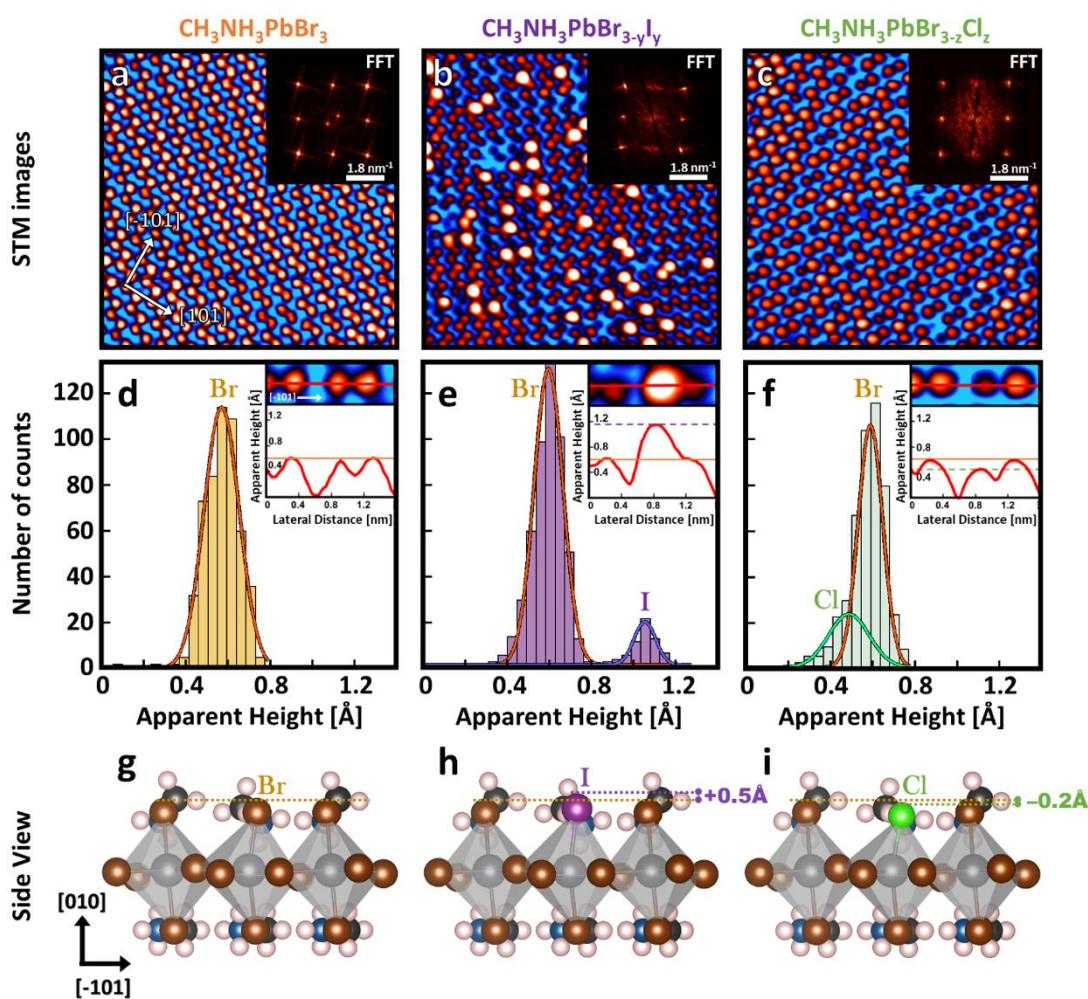


Figure 2. Disordered atomic structure of mixed halide perovskites. (a-c) Large area STM images (10 nm x 10 nm) of the (010) surface of pristine $\text{CH}_3\text{NH}_3\text{PbBr}_3$ (a), and mixed $\text{CH}_3\text{NH}_3\text{PbBr}_{3-y}\text{I}_y$ (b), $\text{CH}_3\text{NH}_3\text{PbBr}_{3-z}\text{Cl}_z$ (c) perovskites. Scan parameters: (a) Bias=+1.3 V, Current=80 pA; (b) +2.0 V, 120 pA; (c) -2.0 V, 100 pA. Inset: Fast Fourier Transform (FFT) obtained from the topographic STM images showing no additional peak at low k-values for the mixed-halide perovskite, suggesting that there is no long-range order of the additional iodine and chlorine ions at the surface. d-f Histogram of the apparent height distribution of local maxima (ions). The main peaks correspond to the Br ions, while the small additional peaks are associated to iodine and chlorine ions (e and f, respectively). Inset: typical profiles obtained for the different halides (Br, I, Cl) at the perovskite surface. g-i Relative positions of the halides with respect to the top $\text{CH}_3\text{NH}_3\text{Br}$ surface. The dash lines in Side View indicate the difference in the STM apparent height for the I ion (+0.5 Å in Figure 2h) and Cl ion (-0.2 Å in Figure 2i) with respect to the Br ion. Color code: Pb (gray), Br (brown), I (purple), Cl (green), C (black), N (light blue), H (white).

1 Additionally, the iodine ions have a larger ionic radius than
 2 bromine. Both the upshift and larger radius contribute to the
 3 observed topographic height increase. In contrast, the chlorine
 4 ions are downshifted and have a smaller ionic radius compared
 5 to Br (Figure 2i) explaining their lower apparent height.

6
 7 Besides the single bright and dark protrusions, which are
 8 attributed to the substitution of Br with I or Cl, we observed
 9 pairs and clusters of bright and dark protrusions (Figure S3).
 10 They are attributed to I or Cl ions that substitute multiple
 11 bromines of the perovskite surface (Figure S4). Two types of
 12 pairs are found on the surface. Iodine and chlorine pairs can
 13 be formed either by substitution of two bromine ions within the
 14 same pair, or by the substitution of two neighboring Br ions
 15 within two adjacent pairs (Figure S3). DFT calculations shows
 16 that the chemical nature of the halides strongly influences the
 17 stability of the pair. The energy barrier for the formation of two
 18 isolated Cl-Br pairs is lower than the energy formation of a
 19 single Cl-Cl pair ($E_{2(\text{Cl-Br})} < E_{\text{Cl-Cl}}$). These results suggest that at
 20 low coverage the chlorine ions prefer to form isolated Cl-Br
 21 pairs rather than clustering together to form Cl-Cl pairs or phase
 22 segregating. The same trend was found for the iodine case, i.e.,
 23 $E_{2(\text{I-Br})} < E_{\text{I-I}}$ (Table S1). This is the reason why the substituting
 24 halide ions were found to be randomly distributed at the surface
 25 of the perovskite, leading to the disordered atomic structure
 26 observed in the experiment.

27 Ultraviolet photoemission spectroscopy (UPS) experiments
 28 were performed on the mixed perovskites to correlate their
 29 atomic structures with their electronic properties (Figure 3).
 30 The valence band (VB) spectra of the perovskite films are
 31 composed of 6 main peaks (A-F) as shown in Figure 3a. A
 32 strong modification of the valence band lineshape can be
 33 observed when substituting bromine ions at the surface with
 34 iodine or chlorine. Based on DFT calculations, we found that
 35 the VB of pristine $\text{CH}_3\text{NH}_3\text{PbBr}_3$ is composed mainly of Br p_x ,
 36 p_y , and p_z hybridized states with a small contribution from the
 37 Pb s and p orbitals (Figure 3b). In addition to these states,
 38 contributions of I and Cl appear in the VB of mixed perovskites.
 39 The substituting halides are responsible for the valence band
 40 modification as observed in the experiment. A higher binding
 41 energy was found for Cl as compared to Br and I (Figure 3b),
 42 in line with the higher stability of the chlorine-mixed perovskite
 43 ($\text{CH}_3\text{NH}_3\text{PbBr}_{3-z}\text{Cl}_z$) as discussed later. Additionally, the
 44 impact of halide substitution on the material work-function was
 45 revealed by UPS. A work-function of 4.77 eV was measured for
 46 pristine $\text{CH}_3\text{NH}_3\text{PbBr}_3$, similar to the values reported in
 47 literature³²⁻³⁴, while a decrease of 0.2 eV of the work function
 48 (ϕ) was observed after chlorine substitution ($\phi = 4.57$ eV).
 49 Interestingly after iodine incorporation in the perovskite film,
 50 the work function was 4.79 eV, closer to the original value of
 51 pristine $\text{CH}_3\text{NH}_3\text{PbBr}_3$ (Figure S5). We found that the work-
 52 function changes originate from a downshift of the vacuum
 53 level induced by a modification of the surface dipole moment
 54 after halide incorporation (Figure S6). A larger dipole moment
 55 amplitude results in a stronger downshift of the vacuum level,
 56 and thus a smaller work function ($\phi_{\text{I}} > \phi_{\text{Br}} > \phi_{\text{Cl}}$). The possibility
 57 of adjusting the work-function as well as the vacuum level
 58 position through halide substitution is of prime interest for
 59 engineering energy level alignment in perovskite-based
 60 devices.

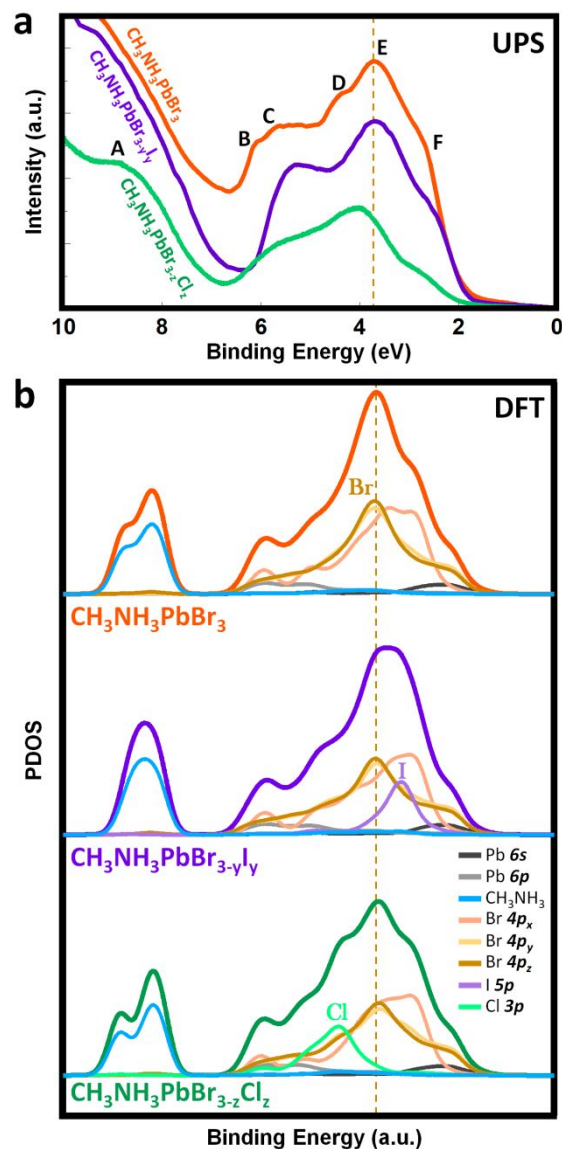


Figure 3. Valence band modification in mixed halide perovskite. a) Experimental ultra-violet photoelectron spectroscopy (UPS) spectra of pure $\text{CH}_3\text{NH}_3\text{PbBr}_3$ (orange) and mixed $\text{CH}_3\text{NH}_3\text{PbBr}_{3-y}\text{I}_y$ (purple); $\text{CH}_3\text{NH}_3\text{PbBr}_{3-z}\text{Cl}_z$ (green) perovskites. b) Calculated PDOS of the pristine and mixed-halide perovskites. The Thick curves represents the summation of all contributions of each orbital indicated by differently colored lines. The PDOS were obtained for the full halide substitution of the perovskite surface.

To further understand the impact of halide substitution on the electronic properties of perovskite materials and its correlation with the stability, we evaluated the changes in the decomposition energy (see Methods) and bandgap of the $\text{CH}_3\text{NH}_3\text{PbBr}_{3-y}\text{I}_y$ and $\text{CH}_3\text{NH}_3\text{PbBr}_{3-z}\text{Cl}_z$ films for different iodine and chlorine ratios. As depicted in Figure 4a, the substitution of bromine ions by iodine at the surface of the perovskite induces a decrease of the decomposition energy (purple curve) and a small but detectable reduction of the band gap (orange curve). In contrast, Figure 4b shows that the incorporation of a small amount of chlorine (below 25%, green curve) leads to an increase of the decomposition energy, with no substantial bandgap changes.

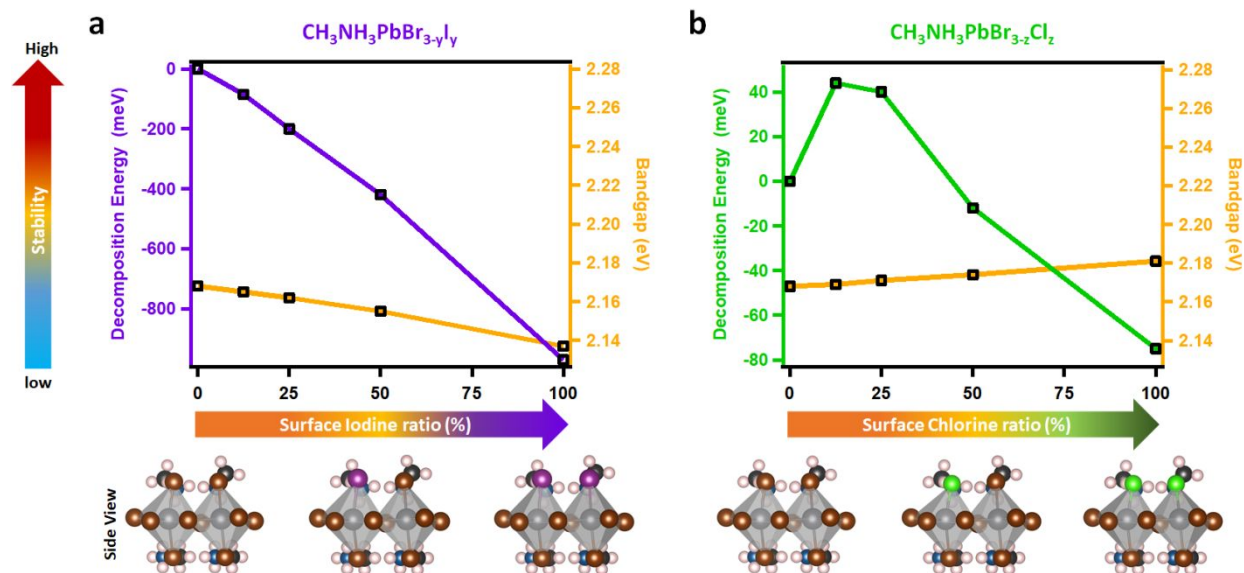


Figure 4. Stability versus bandgap change in mixed perovskite. (a-b) Decomposition energy difference between mixed-halide and pristine perovskite determined by DFT calculations (see methods). a) $\text{CH}_3\text{NH}_3\text{PbBr}_{3-y}\text{I}_y$ with increasing iodine content (y) at the surface. b) $\text{CH}_3\text{NH}_3\text{PbBr}_{3-z}\text{Cl}_z$ with increasing Cl content (z) at the surface. The calculations were performed on a 6 layers slab with only the top layer being substituted. Bottom panels show the atomic structure of the pristine, half mixed, and completely substituted top surface of the perovskite. Color code: Br(brown), I(purple), Cl(green), C(black), N(light blue), H(white).

An increase of the decomposition energy after chlorine substitution suggests higher stability of the perovskite film with respect to external stimuli such as temperature. This stability increase is related to the higher bond strength of Cl-Pb compared to Br-Pb and I-Pb^{35,36}. Beyond the substitution ratio of 25%, the strain induced by the incorporation of the smaller Cl ions with respect to Br counterbalances the benefit of the stronger Cl-Pb bond strength and results in a lowering of the material stability (decomposition energy). Thus, the stability in mixed-halide perovskite results from the interplay between the Pb-halide bond strength that stabilizes the material and the strain induced by the halide substitution that lowers decomposition energy. Based on our results, we suggest that as a general trend, substitution of the original surface halide atoms by a different halide with a smaller ions size and a higher Pb-halide bond strength leads to an increase of the decomposition energy of the system, which in turn increases the material stability. Our DFT finding shows a stability increase without a strong bandgap modification. Although here only the substitution at the surface is considered, these results indicate that there may exist an optimal bulk Cl substitution ratio that would provide higher stability without substantially changing the bandgap of the perovskite material.

To further confirm these findings experimentally, we have studied the stabilization effect of chlorine on an actual solar cell device architecture (Figure S7). First, a 300 nm $\text{CH}_3\text{NH}_3\text{PbBr}_3$ film was spun on a $\text{TiO}_2/\text{FTO}/\text{Glass}$ substrate (see Methods), which resembles the half (up to the perovskite layer) of a standard perovskite solar cell structure. Thereafter, the half-cell architecture was transferred into the UHV system, where chlorine was incorporated into the perovskite film by further PbCl_2 vacuum evaporation. The degradation was then investigated by x-ray photoelectron spectroscopy (XPS) for the half-cell samples with different Cl substitution ratios at the surface (Figure 5). First, the evolution of the Pb $4f$ peak was monitored for the pure $\text{CH}_3\text{NH}_3\text{PbBr}_3$ film without the incorporation of Cl. Figure 5a shows that initially (at $T = 0\text{h}$),

the spectrum is composed of only two peaks at 137.9 and 142.8 eV, attributed to the spin-orbit split Pb $4f_{7/2}$ and Pb $4f_{5/2}$ peaks, later referred to as Pb(2+). After 4h, additional peaks appear at low binding energies associated with the lower oxidation Pb(0) state. Such a state is associated with deterioration of the perovskite film³⁷. Therefore, in the present study we use the Pb(0) peak evolution as an indicator of the perovskite degradation. A progressive and strong increase of the Pb(0) peak intensity is observed as a function of time, indicating that the pure $\text{CH}_3\text{NH}_3\text{PbBr}_3$ film undergoes a fast degradation. In contrast, much slower degradation (i.e., a significantly reduced Pb(0) peak intensity after a given time) was observed for the samples with the additional PbCl_2 evaporation (Figures 5b, 5c). The degradation process is further slowed down as the amount of chlorine substitution increases. When 12% of the Br ions are substituted by Cl at the perovskite surface, the Pb(0) peak emerged after 28h, while it only appears after 116h for a 18% substitution ratio (Figure 5d). For comparison, the substitution at the perovskite surface in the STM image of Figure 2c is about 26%. Substitution ratios were determined by measuring the Cl:Br chemical ratio in XPS. A quantitative analysis of the remaining Pb(2+) species (i.e., undegraded Pb ions on the surface) after a given time is presented in Figure 5e. The results demonstrate experimentally that the incorporation of Cl improves stability of perovskite films. It has been reported that $\text{CH}_3\text{NH}_3\text{PbBr}_3$ shows significantly better stability than $\text{CH}_3\text{NH}_3\text{PbI}_3$ ³⁸. Here in this study, we have shown that with the surface Br ions of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ partially substituted by Cl ions, the half-cell sample stability gets further enhancement. Such a result is expected to have strong implications for device applications. Although the current study focuses on the $\text{CH}_3\text{NH}_3\text{PbBr}_3$ case, the stability increase induced by Cl-incorporation is expected to be even stronger in the $\text{CH}_3\text{NH}_3\text{PbI}_3$ perovskite case, due to a larger difference in bond strength between Pb-Cl and Pb-I when compared to Pb-Cl and Pb-Br. Finding the balance between stability increase and bandgap modification in Cl-incorporated

$\text{CH}_3\text{NH}_3\text{PbI}_3$ is expected to play an important role in optimizing $\text{CH}_3\text{NH}_3\text{PbI}_3$ perovskite-based devices.

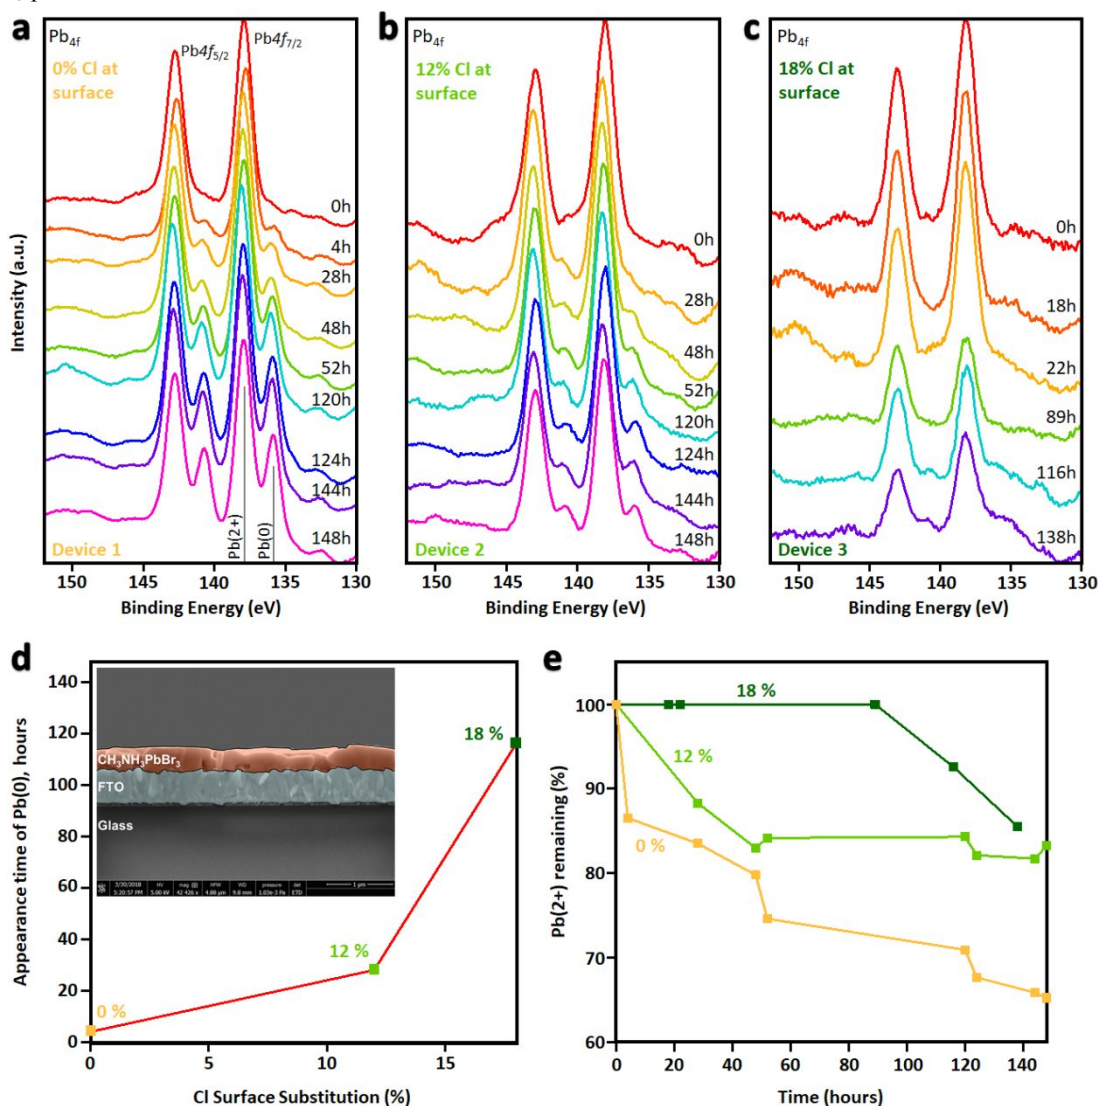


Figure 5. Beneficial aspects of halide mixing on perovskite stability. Time evolution of the Pb 4f peak obtained by x-ray photoelectron spectroscopy (XPS) on a device architecture (a) without addition of chlorine, (b) with 12% of Cl at the surface, and (c) with 18% Cl at the surface. d) Appearance time of Pb(0) feature with respect to the Cl substitution ratio at the surface. e) Time evolution of the percentage of Pb(2+) remaining for the different Cl substitution ratio at the surface.

CONCLUSION

We have determined for the first time the surface atomic structure of $\text{CH}_3\text{NH}_3\text{PbBr}_{3-y}\text{I}_y$ and $\text{CH}_3\text{NH}_3\text{PbBr}_{3-z}\text{Cl}_z$ mixed-halide perovskite in real space and correlate it to a corresponding enhancement or degradation of the stability of the compound. Using scanning tunneling microscopy combined with density functional theory we find that Br ions are replaced by the halide ions. The substituted halides are randomly distributed at the surface, showing a disordered atomic structure with no phase segregation. For the low substitution ratio (below 25%), Cl and I affect in opposing ways to the work function and stability of the mixed perovskite. Our studies on device architectures demonstrate that the stability is increased after incorporating 12–18% of Cl, which agrees with the calculated increase of the decomposition energy. Our results suggest that there is an optimal ratio of chlorine substitution which provides

a maximum increase in stability without significant bandgap modification. This balance is an important direction for future device research, to address the perovskite stability issue, which remains as one of the main challenges for industrial application.


METHODS

Surface characterization. $\text{CH}_3\text{NH}_3\text{PbBr}_3$ perovskite films were grown on Au(111) single crystal using molecular beam epitaxy, following previously reported method²⁸. Vacuum deposition techniques have been used to fabricate perovskite solar cell devices with similar power conversion efficiencies to those fabricated by solution-based deposition methods³⁹⁻⁴¹. In addition, the use of vacuum deposition techniques ensures the sample's cleanliness and high purity (e.g., free from solvent molecules), which facilitates further atomically precise characterization with scanning tunneling microscopy. First, the gold sample was cleaned in an ultrahigh vacuum environment

($\sim 1 \times 10^{-9}$ torr) with several cycles of Ne^+ sputtering followed by subsequent annealing at 773 K for 5 min. Thereafter, $\text{CH}_3\text{NH}_3\text{PbBr}_3$ was obtained by the co-deposition of $\text{CH}_3\text{NH}_3\text{Br}$ and PbBr_2 molecules at 361 K and 498 K respectively for 10 min. During deposition, the gold surface was kept at 130 K to ensure the adhesion of the methyl-ammonium compound (MA). Mixed perovskites were obtained by sublimating PbI_2 and PbCl_2 on the $\text{CH}_3\text{NH}_3\text{PbBr}_3$ film from Knudsen cells held at 525 K and 560 K respectively. During sublimation, the sample was kept at room temperature. Low-temperature scanning tunneling microscopy (LT-STM) was used to characterize the atomic-scale structures of the different perovskite ultra-thin films. The STM measurements were performed at 5 K. A cut Pt/Ir tip was used to acquire the STM images. The bias voltage was applied to the sample. X-ray photoelectron spectroscopy (XPS) and ultraviolet photoelectron spectroscopy (UPS) were performed in the same ultra-high vacuum (UHV) setup as the STM measurements, preventing any contamination from air.

Density functional theory. The calculations were performed using the VASP code⁴²⁻⁴⁴ with the projector augmented wave (PAW)⁴⁵ potential and Perdew–Burke–Ernzerhof (PBE)⁴⁶ exchange-correlation functional. For the unit cell, Brillouin zone (BZ) sampling was done using a $4 \times 4 \times 4$ Monkhorst–Pack grid. The $\text{CH}_3\text{NH}_3\text{PbBr}_3$ (010) surfaces were modeled using (2×2) slabs containing six atomic layers. The size of the supercell was $(16.24 \times 16.54 \times 35.52)$ Å. A large vacuum thickness of 20 Å along the direction normal to the surface was employed to separate surfaces from their periodic images. The bottom four layers of atoms were kept fixed at their optimized bulk positions. All other atoms were fully relaxed until the forces on each atom were smaller than 0.01 eV/Å. The nonlocal van der Waals interactions were evaluated with the optB86-vdW functional⁴⁷. The Gamma-centered Monkhorst–Pack sampling of $3 \times 3 \times 1$ was adopted to study the electronic properties of the surfaces of $\text{CH}_3\text{NH}_3\text{PbBr}_3$ (MAPbBr₃). From the electronic ground-state structure, STM images were calculated with the p4vasp code.

To evaluate the stability of the mixed perovskite, we consider the following reaction:



Where X is Cl or I, and y/3 is its ratio. The decomposition energy of the mixed perovskite $2\text{MAPbBr}_{3-y}\text{X}_y$ is calculated as:

$$E_{\text{dec}} = E(\text{MAPbBr}_{3-y}\text{X}_y) - E(\text{MAPbBr}_3) + \frac{y}{2}[E(\text{PbBr}_2) - E(\text{PbX}_2)]$$

The stability of the perovskite is characterized by the decomposition energy (E_{dec}). The larger the decomposition energy, the more stable the material is.

Device fabrication. The patterned FTO glass (Pilkington, TEC-8, 8Ω/sq) was cleaned with detergent and DI water and sonicated with ethanol in an ultrasonic bath for 20 min. UV-Ozone was treated for 15 min prior to use. The mesoporous TiO_2 (ca. 50 nm) layer was deposited by spin coating at 2000 rpm for 20 s (acceleration was 500 rpm/s) using the diluted TiO_2 solution in 1-butanol⁴⁸. The deposited TiO_2 film was annealed at 550 °C for 30 min. The $\text{CH}_3\text{NH}_3\text{PbBr}_3$ film was prepared via adduct method⁴⁹. 0.367g of PbBr_2 (TCI) and 0.112 $\text{CH}_3\text{NH}_3\text{Br}$ (Dyesol) were dissolved in 0.6 mL of DMF with 75 μL of

DMSO at 60 °C. The $\text{CH}_3\text{NH}_3\text{Br}_3$ solution was spin-coated on the mp- TiO_2 substrate at 4000 rpm for 20 and 0.3 mL of diethyl ether was poured when 10 s was remained. Then, it was dried on a hot plate at 100 °C for 20 min.

ASSOCIATED CONTENT

Supporting Information:

1. Adsorption vs substitution in mixed-halide perovskite
2. Halide pairs and clusters at the surface of mixed perovskites
3. Determination of the valence band maximum (VBM)
4. Electrostatic potential and work-function changes
5. Device architecture

This material is available free of charge via the Internet at <http://pubs.acs.org>.

AUTHOR INFORMATION

Corresponding Author

* Yabing.Qi@OIST.jp

* Yanfa.Yan@utoledo.edu

Present Addresses

†Department Physik, Universität Siegen, 57068 Siegen, Germany.

ORCID IDs

Jeremy Hieulle: 0000-0003-4891-4007
 Xiaoming Wang: 0000-0002-5438-1334
 Collin Stecker: 0000-0003-4247-5699
 Dae-Yong Son: 0000-0001-6898-5326
 Longbin Qiu: 0000-0002-7696-4901
 Robin Ohmann: 0000-0003-2483-1282
 Luis K. Ono: 0000-0003-3176-1876
 Aitor Mugarza: 0000-0002-2698-885X
 Yanfa Yan: 0000-0003-3977-5789
 Yabing Qi: 0000-0002-4876-8049

Author Contributions

The manuscript was written through contributions of all authors. All authors have given approval to the final version of the manuscript. ‡These authors contributed equally.

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENT

This work was supported by funding from the Energy Materials and Surface Sciences Unit of the Okinawa Institute of Science and Technology Graduate University, the OIST R&D Cluster Research Program, the OIST Proof of Concept (POC) Program, and JSPS KAKENHI Grant Number JP18K05266. The work at The University of Toledo was supported by the Center for Hybrid Organic Inorganic Semiconductors for Energy (CHOISE), an Energy Frontier Research Center funded by the Office of Basic Energy Sciences, Office of Science within the US Department of Energy. The theoretical calculation part used the resources of the National Energy Research Scientific Computing Center, which is supported by the Office of Science of the U.S. Department of Energy under Contract No. DE-AC02-05CH11231.

ABBREVIATIONS

STM, scanning tunneling microscope; DFT, density functional theory; XPS, x-ray photoelectron spectroscopy; UPS, ultraviolet photoemission spectroscopy; FFT, fast Fourier transform; MA, methylammonium CH_3NH_3 .

REFERENCES

- (1) National Renewable Energy Laboratory (NREL). URL: <https://www.nrel.gov/pv/assets/pdfs/pv-efficiency-chart.20190103.pdf> (access date: 3rd Jan. 2019).
- (2) Noh, J.H.; Im, S.H.; Heo, J.H.; Mandal, T.N.; Seok, S.I. Chemical management for colorful, efficient, and stable inorganic-organic hybrid nanostructured solar cells. *Nano Letters* **2013**, *13*, 1764.
- (3) Bush, K. A.; Palmstrom, A.F.; Yu, Z.J.; Boccard, M.; Cheacharoen, R.; Mailoa, J.P.; McMeekin, D.P.; Hoye, R.L.Z.; Bailie, C.D.; Leijtens, T.; Peters, I.M.; Minichetti, M.C.; Rolston, N.; Prasanna, R.; Sofia, S.; Harwood, D.; Ma, W.; Moghadam, F.; Snaith, H.J.; Buonassisi, T.; Holman, Z.C.; Bent, S.F.; McGehee, M.D. 23.6%-efficient monolithic perovskite/silicon tandem solar cells with improved stability. *Nat. Energy* **2017**, *2*, 17009.
- (4) Jiang, F.; Rong, Y.; Liu, H.; Liu, T.; Mao, L.; Meng, W.; Qin, F.; Jiang, Y.; Luo, B.; Xiong, S.; Tong, J.; Liu, Y.; Li, Z.; Han, H.; Zhou, Y. Synergistic effect of PbI₂ passivation and chlorine inclusion yielding high open-circuit voltage exceeding 1.15 V in both mesoscopic and inverted planar CH₃NH₃PbI₃(Cl)-based perovskite solar cells. *Adv. Funct. Mater.* **2016**, *26*, 8119.
- (5) Liu, J.; Prezhdo, O.V. Chlorine doping reduces electron-hole recombination in lead iodide perovskites: time-domain ab initio analysis. *J. Phys. Chem. Lett.* **2015**, *6*, 4463.
- (6) Yu, H.; Wang, F.; Xie, F.; Li, W.; Chen, J.; Zhao, N. The role of chlorine in the formation process of “CH₃NH₃PbI_{3-x}Cl_x” perovskite. *Adv. Funct. Mater.* **2014**, *24*, 7102.
- (7) Chen, Q.; Zhou, H.; Fang, Y.; Stieg, A.Z.; Song, T.-B.; Wang, H.-H.; Xu, X.; Liu, Y.; Lu, S.; You, J.; Sun, P.; McKay, J.; Goorsky, M.S.; Yang, Y. The optoelectronic role of chlorine in CH₃NH₃PbI₃(Cl)-based perovskite solar cells. *Nat. Commun.* **2015**, *6*, 7269.
- (8) Quarti, C.; Mosconi, E.; Umari, P.; De Angelis, F. Chlorine incorporation in the CH₃NH₃PbI₃ perovskite: small concentration, big effect. *Inorg. Chem.* **2017**, *56*, 74.
- (9) Colella, S.; Mosconi, E.; Pellegrino, G.; Alberti, A.; Guerra, V.L.P.; Masi, S.; Listorti, A.; Rizzo, A.; Condorelli, G.G.; De Angelis, F.; Gigli, G. Elusive presence of chloride in mixed halide perovskite solar cells. *J. Phys. Chem. Lett.* **2014**, *5*, 3532.
- (10) Jeon, N.J.; Noh, J.H.; Kim, Y.C.; Yang, W.S.; Ryu, S.; Seok, S.I. Solvent engineering for high-performance inorganic-organic hybrid perovskite solar cells. *Nat. Mater.* **2014**, *13*, 897.
- (11) Lee, M.M.; Teuscher, J.; Miyasaka, T.; Murakami, T.N.; Snaith, H.J. Efficient hybrid solar cells based on meso-superstructured organometal halide perovskites. *Science* **2012**, *338*, 643.
- (12) Zhang, M.; Yu, H.; Lyu, M.; Wang, Q.; Yun, J.-H.; Wang, L. Composition-dependent photoluminescence intensity and prolonged recombination lifetime of perovskite CH₃NH₃PbBr_{3-x}Cl_x films. *Chem. Commun.* **2014**, *50*, 11727.
- (13) Edri, E.; Kirmayer, S.; Cahen, D.; Hodes, G. High open-circuit voltage solar cells based on organic-inorganic lead bromide perovskite. *J. Phys. Chem. Lett.* **2013**, *4*, 897.
- (14) Edri, E.; Kirmayer, S.; Kulbak, M.; Hodes, G.; Cahen, D. Chloride inclusion and hole transport material doping to improve methyl ammonium lead bromide perovskite-based high open-circuit voltage solar cells. *J. Phys. Chem. Lett.* **2014**, *5*, 429.
- (15) Ono, L.K.; Juarez-Perez, E.J.; Qi, Y.B. Progress on perovskite materials and solar cells with mixed cations and halide anions. *ACS Appl. Mater. Interfaces* **2017**, *9*, 30197.
- (16) Zhou, Y.; Zhou, Z.; Chen, M.; Zong, Y.; Huang, J.; Pang, S.; Padture, N.P. Doping and alloying for improved perovskite solar cells. *J. Mater. Chem. A* **2016**, *4*, 17623.
- (17) Yin, W.-J.; Yang, J.-H.; Kang, J.; Yan, Y.; Wei, S.-H. Halide perovskite materials for solar cells: a theoretical review. *J. Mater. Chem. A* **2015**, *3*, 8926.
- (18) Ye, M.; Hong, X.; Zhang, F.; Liu, X. Recent advancements in perovskite solar cells: flexibility, stability and large scale. *J. Mater. Chem. A* **2016**, *4*, 6755.
- (19) Pool, V.L.; Gold-Parker, A.; McGehee, M.D.; Toney, M.F. Chlorine in PbCl₂-derived hybrid-perovskite solar absorbers. *Chem. Mater.* **2015**, *27*, 7240.
- (20) Luo, S.; Daoud, W.A. Crystal structure formation of CH₃NH₃PbI_{3-x}Cl_x perovskite. *Materials* **2016**, *9*, 123.
- (21) Zhang, T.; Yang, M.; Benson, E.E.; Li, Z.; Lagemaat, J.; Luther, J.M.; Yan, Y.; Zhu, K.; Zhao, Y. A facile solvothermal growth of single crystal mixed halide perovskite CH₃NH₃Pb(Br_{1-x}Cl_x)₃. *Chem. Commun.* **2015**, *51*, 7820.
- (22) Ono, L.K.; Qi, Y.B. Surface and interface aspects of organometal halide perovskite materials and solar cells. *J. Phys. Chem. Lett.* **2016**, *7*, 4764.
- (23) Wang, S.; Sakurai, T.; Wen, W.; Qi, Y.B. Energy level alignment at interfaces in metal halide perovskite solar cells. *Adv. Mater. Interfaces* **2018**, 1800260.
- (24) Hawash, Z.; Raga, S.R.; Son, D.-Y.; Ono, L.K.; Park, N.-G.; Qi, Y.B. Interfacial modification of perovskite solar cells using an ultrathin MAI layer leads to enhanced energy level alignment, efficiencies, and reproducibility. *J. Phys. Chem. Lett.* **2017**, *8*, 3947.
- (25) Jhuo, H.-J.; Yeh, P.-N.; Liao, S.-H.; Li, Y.-L.; Sharma, S.; Chen, S.-A. Inverted perovskite solar cells with inserted cross-linked electron-blocking interlayers for performance enhancement. *J. Mater. Chem. A* **2015**, *3*, 9291.
- (26) Liu, Y.; Bag, M.; Renna, L.A.; Page, Z.A.; Kim, P.; Emrick, T.; Venkataraman, D.; Russell, T.P. Understanding interface engineering for high-performance fullerene/perovskite planar heterojunction solar cells. *Adv. Energy Mater.* **2016**, *6*, 1501606.
- (27) Zhang, Y.; Liu, M.; Eperon, G.E.; Leijtens, T.C.; McMeekin, D.; Saliba, M.; Zhang, W.; de Bastiani, M.; Petrozza, A.M.; Herz, L.M.; Johnston, M.B.; Lin, H.; Snaith, H.J. Charge selective contacts, mobile ions and anomalous hysteresis in organic-inorganic perovskite solar cells. *Mater. Horiz.* **2015**, *2*, 315.
- (28) Ono, L.K.; Wang, S.; Kato, Y.; Raga, S.R.; Qi, Y.B. Fabrication of semi-transparent perovskite films with centimeter-scale superior uniformity by the hybrid deposition method. *Energy Environ. Sci.* **2014**, *7*, 3989.
- (29) Ohmann, R.; Ono, L.K.; Kim, H.-S.; Lin, H.; Lee, M.V.; Li, Y.; Park, N.-G.; Qi, Y.B. Real-space imaging of the atomic structure of organic-inorganic perovskite. *J. Am. Chem. Soc.* **2015**, *137*, 16049.
- (30) Hieulle, J.; Stecker, C.; Ohmann, R.; Ono, L.K.; Qi, Y.B. Scanning probe microscopy applied to organic-inorganic halide perovskite materials and solar cells. *Small Methods* **2018**, *2*, 1700295.
- (31) She, L.; Liu, M.; Zhong, D. Atomic structures of CH₃NH₃PbI₃(001) surfaces. *ACS Nano* **2016**, *10*, 1126.
- (32) Kedem, N.; Kulbak, M.; Brenner, T.M.; Hodes, G.; Cahen, D. Type-inversion as a working mechanism of high voltage MAPbBr₃(Cl)-based halide perovskite solar cells. *Phys. Chem. Chem. Phys.* **2017**, *19*, 5753.
- (33) Olthof, S.; Meerholz, K. Substrate-dependent electronic structure and film formation of MAPbI₃ perovskites. *Sci. Rep.* **2017**, *7*, 40267.
- (34) Comin, R.; Walters, G.; Thibau, E.S.; Voznyy, O.; Lu, Z.-H.; Sargent, E.H. Structural, optical, and electronic studies of wide-bandgap lead halide perovskites. *J. Mater. Chem. C* **2015**, *3*, 8839.
- (35) Darwent, B. deB. National Standard Reference Data Series. *National Bureau of Standards, Washington, D.C.* **1970**, 31.
- (36) Cottrell, T.L. *The Strengths of Chemical Bonds*, 2nd Edition, Butterworth, London **1958**.
- (37) Juarez-Perez, E.J.; Ono, L.K.; Maeda, M.; Jiang, Y.; Hawash, Z.; Qi, Y.B. Photodecomposition and thermal decomposition in methylammonium halide lead perovskites and inferred design principles to increase photovoltaic device stability. *J. Mater. Chem. A* **2018**, *6*, 9604.
- (38) Pont, S.; Bryant, D.; Lin, C.-T.; Aristidou, N.; Wheeler, S.; Ma, X.; Godin, R.; Haque, S.A.; Durrant, J.R. Tuning CH₃NH₃Pb(I_{1-x}Br_x)₃

- perovskite oxygen stability in thin films and solar cells. *J. Mater. Chem. A* **2017**, *5*, 9553.
- (39) Liu, M.Z.; Johnston, M.B.; Snaith, H.J.; Efficient planar heterojunction perovskite solar cells by vapour deposition. *Nature* **2013**, *501*, 395.
- (40) Malinkiewicz, O.; Yella, A.; Lee, Y.H.; Miguez Espallargas, G.; Grätzel, M.; Nazeeruddin, M.K.; Bolink, H.J.; Perovskite solar cells employing organic charge-transport layers. *Nature Photonics* **2014**, *8*, 128.
- (41) Momblona, C.; Gil-Escrig, L.; Bandiello, E.; Hutter, E.M.; Sessolo, M.; Lederer, K.; Blochwitz-Nimoth, J.; Bolink, H.J. Efficient vacuum deposited p-i-n and n-i-p perovskite solar cells employing doped charge transport layers. *Energy Environ. Sci.* **2016**, *9*, 3456.
- (42) Kresse, G.; Hafner, J. Ab initio. *Phys. Rev. B* **1993**, *47*, 558.
- (43) Kresse, G.; Furthmüller, J. Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set. *Comput. Mater. Sci.* **1996**, *6*, 15.
- (44) Kresse, G.; Furthmüller, J. Efficient iterative schemes for ab initio total-energy calculations using a plane-wave basis set. *Phys. Rev. B* **1996**, *54*, 11169.
- (45) Blöchl, P.E. Projector augmented-wave method. *Phys. Rev. B* **1994**, *50*, 17953.
- (46) Perdew, J.P.; Burke, K.; Ernzerhof, M. Generalized gradient approximation made simple. *Phys. Rev. Lett.* **1996**, *77*, 3865.
- (47) Klimeš, J.; Bowler, D.R.; Michaelides, A. Van der Waals density functionals applied to solids. *Phys. Rev. B* **2011**, *83*, 195131.
- (48) Son, D.-Y.; Lee, J.W.; Choi, Y.J.; Jang, I.H.; Lee, S.; Yoo, P.J.; Shin, H.; Ahn, N.; Choi, M.; Kim, D.; Park, N.-G. Self-formed grain boundary healing layer for highly efficient CH₃NH₃PbI₃ perovskite solar cells. *Nat. Energy*. **2016**, *1*, 16081.
- (49) Ahn, N.; Son, D.-Y.; Jang, I.H.; Kang, S.M.; Choi, M.; Park, N.-G. Highly reproducible perovskite solar cells with average efficiency of 18.3% and best efficiency of 19.7% fabricated via Lewis base adduct of lead(II) iodide. *J. Am. Chem. Soc.* **2015**, *137*, 8696.

TOC Graph

